



# Assembly Precautions for the Nichia 131G/131H Series LEDs

## Table of Contents



1. <u>LED Outline Dimensions/Tape Dimensions</u>	2-5
2. <u>Handling Precautions</u>	6
3. <u>Design Recommendations for Optimal Amount of Solder</u>	7
4. <u>Precautions for Setting Up a Pick-and-Place Machine/Nozzle</u>	8-12
5. <u>Precautions When Reflow Soldering</u>	12
6. <u>Evaluation of the Effect of Solder Conditions</u>	13-19

The Nichia part numbers NCSA131G, NCSA131H, NCSW131G, NCSW131H, NCSW131G-SA, NCSW131H-SA, NCSW131G-SB, and NCSW131H-SB within this document are merely Nichia’s part numbers for those Nichia products and are not related nor bear resemblance to any other company’s product that might bear a trademark.

This document contains tentative information, Nichia may change the contents without notice.

## 1. LED Outline Dimensions/Tape Dimensions



Table 1. NCSA131G / NCSA131H Product Specifications

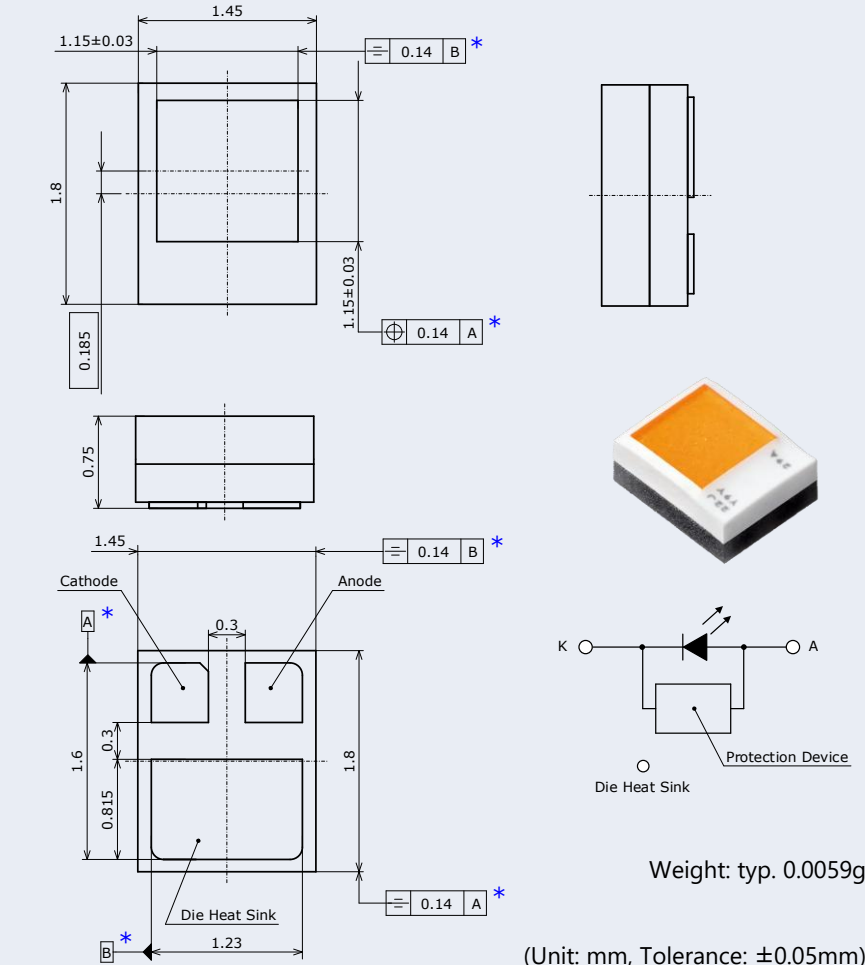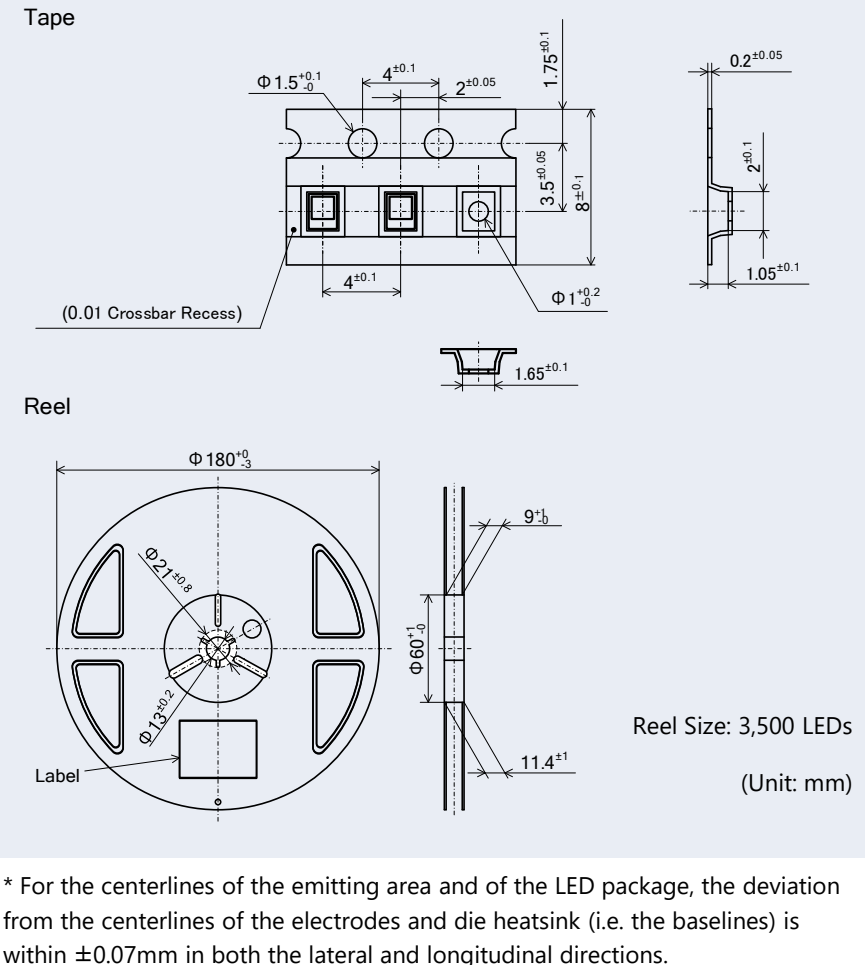LED	Embossed Carrier Tape
 <p>LED package dimensions and diagrams. The package is rectangular with a width of 1.45 mm and a height of 1.8 mm. The distance between the centerlines of the electrodes is 1.15 ± 0.03 mm. The package is shown from top, side, and perspective views. A top view shows the cathode (A) and anode (B) electrodes, with a die heat sink in the center. A side view shows the package height and the distance from the top surface to the centerline of the electrodes (0.185 mm). A perspective view shows the package with a yellow emitting area. A circuit diagram shows the LED connected to a protection device and a die heat sink. The weight is typ. 0.0059g. Dimensions are in mm, tolerance is ±0.05mm.</p> <p>Weight: typ. 0.0059g (Unit: mm, Tolerance: ±0.05mm)</p>	 <p>Embossed carrier tape and reel dimensions. The tape has a width of 1.65 ± 0.1 mm. The distance between the centerlines of the LEDs is 4 ± 0.1 mm. The distance between the centerlines of the electrodes is 2 ± 0.05 mm. The distance from the top surface to the centerline of the electrodes is 1.75 ± 0.1 mm. The diameter of the LED is Φ1.5<sup>+0.1</sup><sub>-0</sub> mm. The diameter of the electrode is Φ1<sup>+0.2</sup><sub>-0</sub> mm. The diameter of the die heat sink is Φ3<sup>+0.2</sup> mm. The diameter of the reel is Φ180<sup>0</sup><sub>-3</sub> mm. The reel has a width of 60 ± 0 mm. The reel has a length of 11.4 ± 1 mm. The reel size is 3,500 LEDs. The unit is mm.</p> <p>Reel Size: 3,500 LEDs (Unit: mm)</p> <p>* For the centerlines of the emitting area and of the LED package, the deviation from the centerlines of the electrodes and die heatsink (i.e. the baselines) is within ±0.07mm in both the lateral and longitudinal directions.</p>

This document contains tentative information, Nichia may change the contents without notice.

## 1. LED Outline Dimensions/Tape Dimensions


Table 2. NCSW131G / NCSW131H Product Specifications

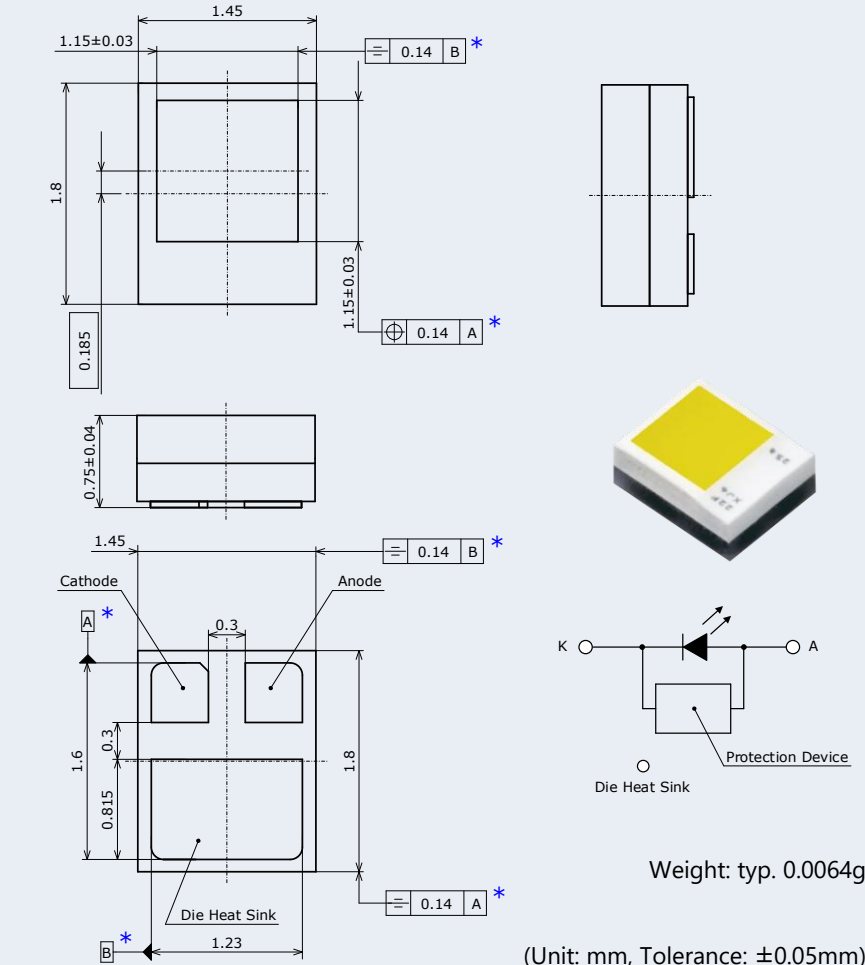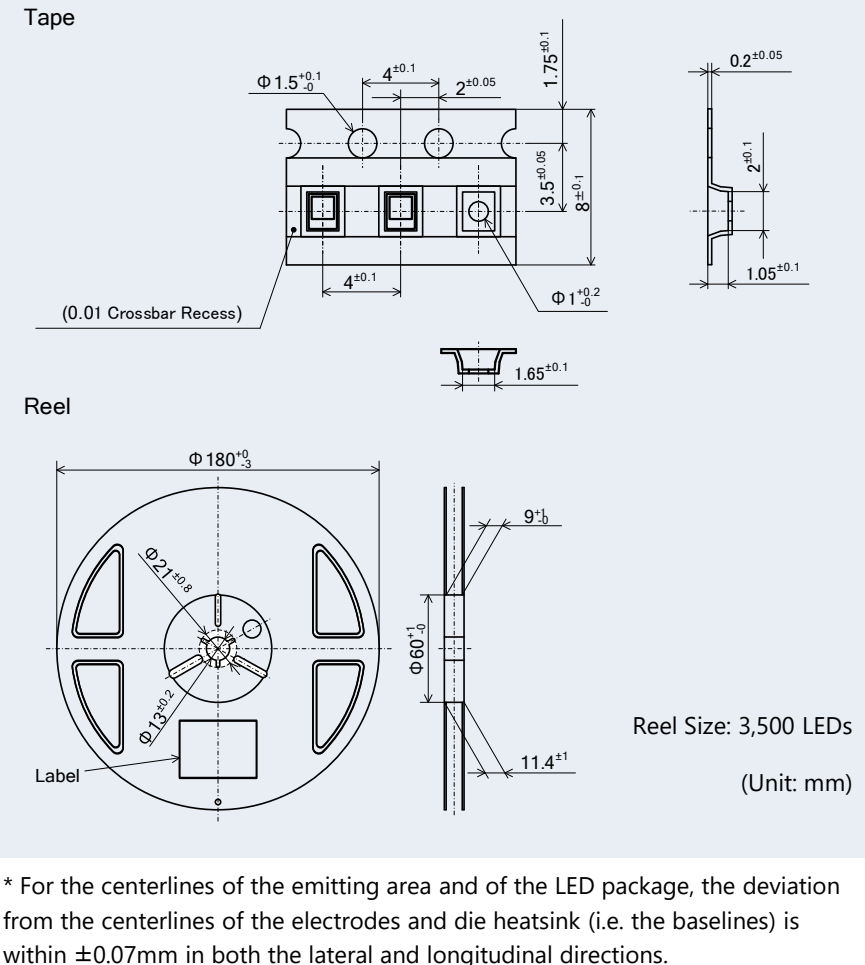LED	Embossed Carrier Tape
 <p>LED package dimensions and diagrams. The package is 1.45 mm wide and 1.8 mm high. The emitting area is 1.15 ± 0.03 mm wide and 0.75 ± 0.04 mm high. The cathode is on the left and the anode is on the right. The package includes a die heat sink and a protection device. The weight is typically 0.0064g. Dimensions are in mm, tolerance is ±0.05mm.</p> <p>Weight: typ. 0.0064g (Unit: mm, Tolerance: ±0.05mm)</p>	 <p>Embossed carrier tape dimensions and diagrams. The tape has a width of 1.65 ± 0.1 mm. The pitch between LEDs is 4 ± 0.1 mm. The LED diameter is 1.5 ± 0.1 mm. The tape has a thickness of 0.2 ± 0.05 mm. The reel diameter is 180 ± 0.3 mm. The reel has 3,500 LEDs. Dimensions are in mm, tolerance is ±0.05mm.</p> <p>Reel Size: 3,500 LEDs (Unit: mm)</p> <p>* For the centerlines of the emitting area and of the LED package, the deviation from the centerlines of the electrodes and die heatsink (i.e. the baselines) is within ±0.07mm in both the lateral and longitudinal directions.</p>

This document contains tentative information, Nichia may change the contents without notice.

## 1. LED Outline Dimensions/Tape Dimensions

Table 3. NCSW131G-SA / NCSW131H-SA Product Specifications

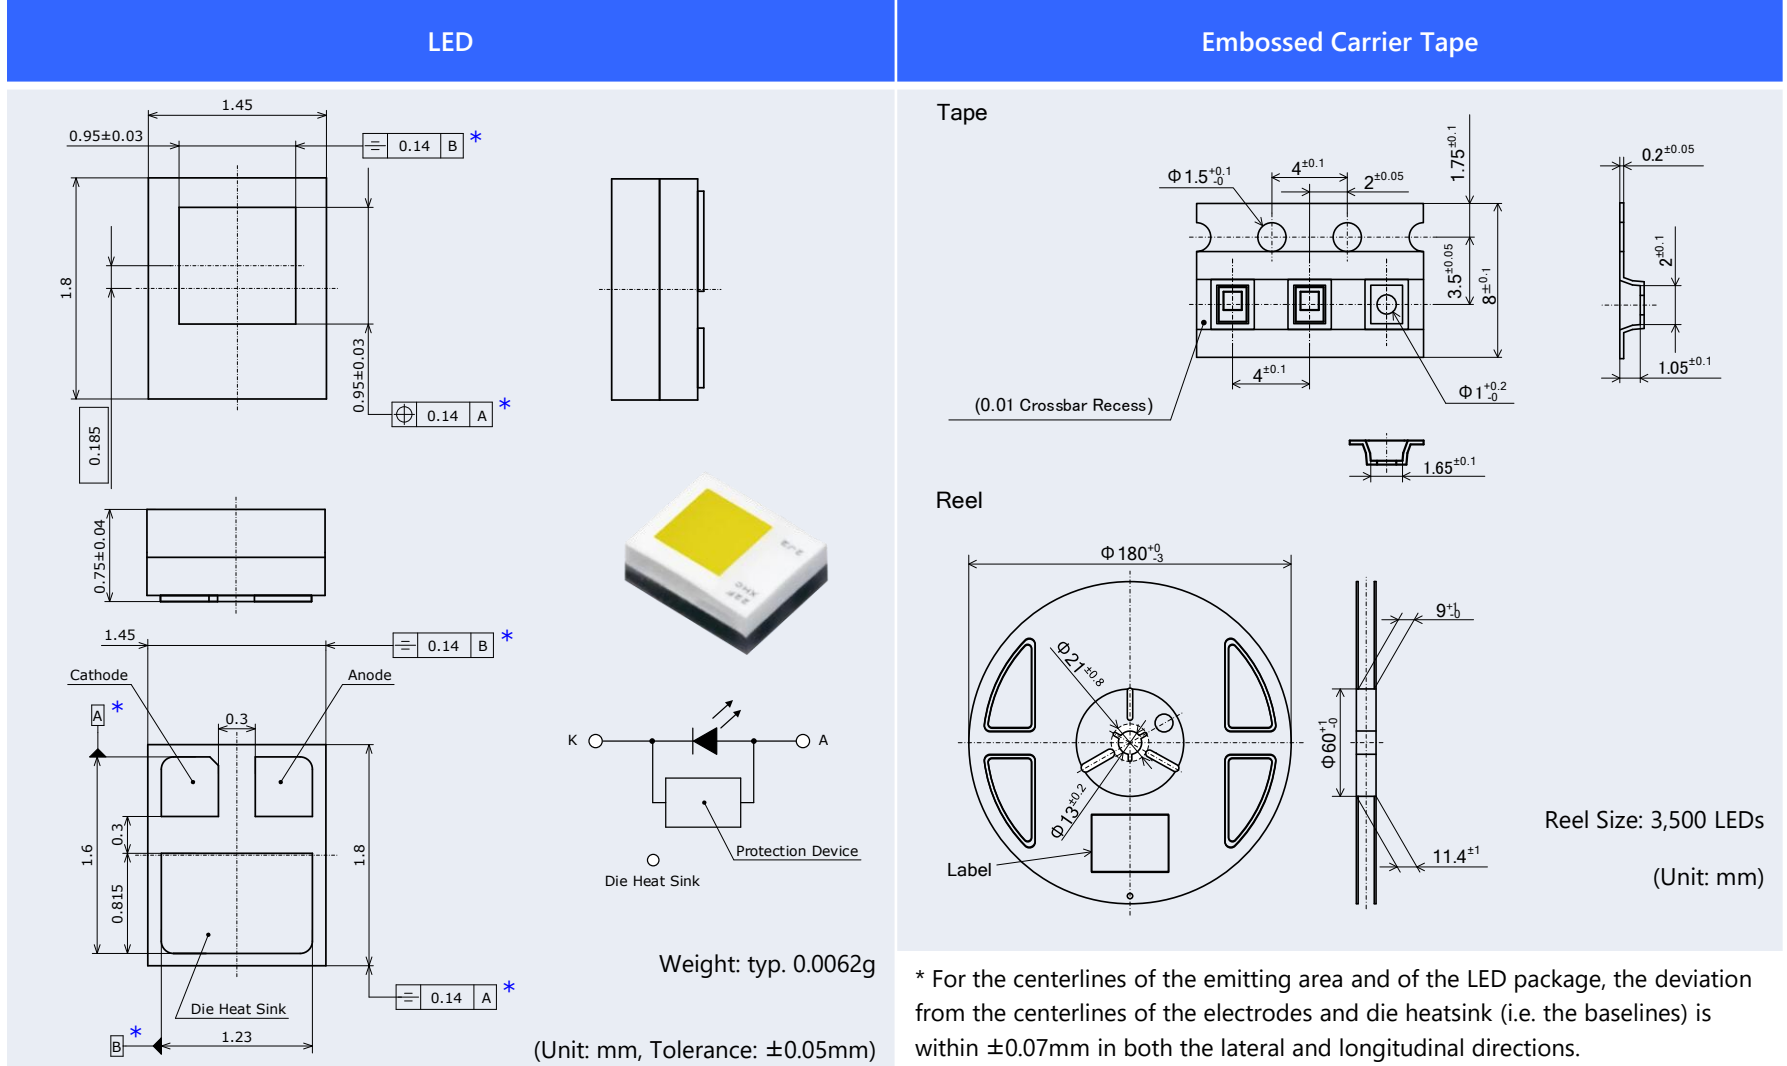

This document contains tentative information, Nichia may change the contents without notice.



## 2. Handling Precautions

### 2.1 Handling with bare hands

Do not handle the LEDs with bare hands. This may contaminate the LED surface and have an effect on the optical characteristics.

### 2.2 Handling with tweezers

Ensure that when handling the LEDs with tweezers, grab/hold the LEDs by the sides of the ceramic substrate and ensure that excessive force is not applied to the LEDs. Otherwise, it may cause damage to the light emitting area and/or the silicone resin (e.g. cut, scratch, chip, crack, etc.) and have an effect on the optical characteristics and/or the reliability.

### 2.3 Stacking assembled PCBs together

Do not stack assembled PCBs together. Otherwise, it may cause damage to the light emitting area (e.g. cut, scratch, chip, crack, etc.) and have an effect on the optical characteristics and/or the reliability.

### 2.4 ESD Precautions

The LEDs are sensitive to transient excessive voltages (e.g. ESD, lightning surge). If this excessive voltage occurs in the circuit, it may cause the LEDs to be damaged causing issues (e.g. the LEDs to become dimmer or not to illuminate [i.e. catastrophic failure]). When handling the LEDs, ensure that necessary measures have been taken to protect them from transient excess voltages. Refer to the applicable specification for more details.

### 2.5 Storage Conditions

The storage/packaging requirements for the Nichia 131G/131H Series LEDs are comparable to JEDEC Moisture Sensitivity Level (MSL) 2 or equivalent. Nichia used IPC/JEDEC STD-020 as a reference to rate the MSL of the LEDs.

Table 5. Storage Conditions

Conditions		Temperature	Humidity	Time
Storage	Before Opening Aluminum Bag	≤ 30°C	≤ 90%RH	Within 1 Year from Delivery Date
	After Opening Aluminum Bag	≤ 30°C	≤ 70%RH	≤ 1 Year

✓ Correct




Suggestion: Grab/hold the LEDs with tweezers by the sides of the ceramic substrate.

✗ Incorrect



Caution: Do not touch the emitting area.

✗ Incorrect

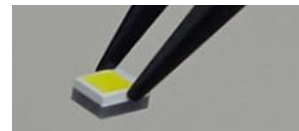

Caution: Do not touch the silicone resin.

Figure 1. Correct/Incorrect Examples of Handling with Tweezers



Figure 2. Example of a Damaged Silicone Resin

This document contains tentative information, Nichia may change the contents without notice.

### 3. Design Recommendations for Optimal Amount of Solder Soldering Pad Pattern/Metal Solder Stencil Aperture

Table 6. Recommended Soldering Pad Pattern/Metal Solder Stencil Aperture

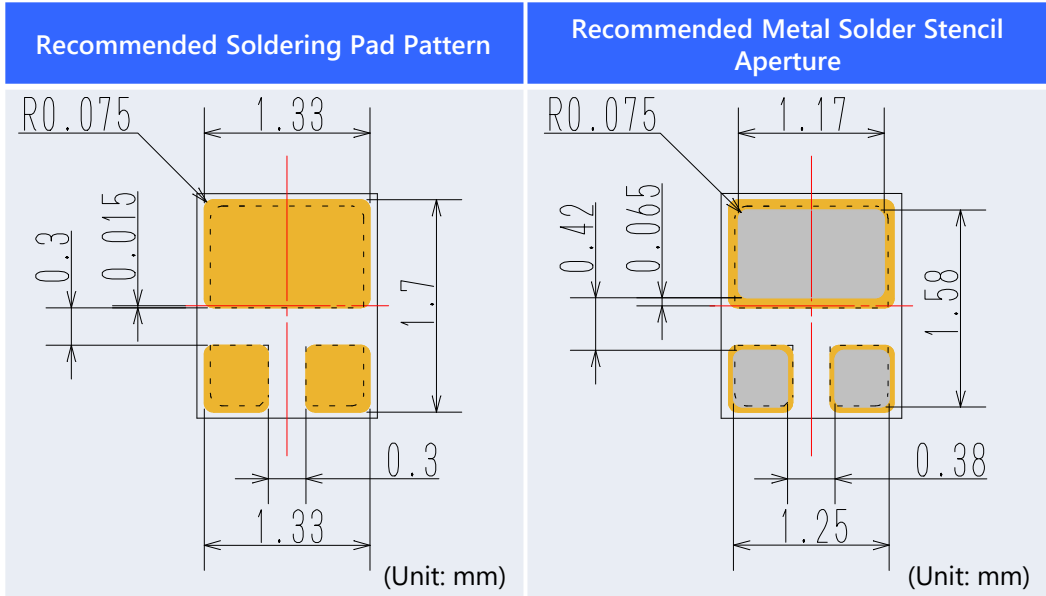







Table 7. Recommended Solder/Metal Solder Stencil Conditions

Item	Recommended Conditions
Metal Solder Stencil (Thickness)	100 (μm)
Solder Paste (Composition)	Sn-3.0Ag-0.5Cu

-  LED Outline
-  Electrodes and Die Heat Sink
-  Center of the Soldering Pad Pattern
-  Soldering Pad Pattern
-  Metal Solder Stencil Aperture

The recommended soldering pad pattern, metal solder stencil aperture, and thickness of the metal solder stencil provided in Tables 6 and 7 have been determined under Nichia’s conditions: ensure that there are no issues with the chosen assembly conditions prior to use.

If the solder paste and/or the PCB (e.g. base material, insulation material, soldering pad patterns, etc.) are not appropriate, it may cause thermal stress in the solder joints resulting in cracks. A thorough verification should be performed at the finished product level with the chosen solder paste and PCB prior to use to ensure there are no issues. In order to reduce the possibility of solder cracks, Nichia recommends using a copper-core PCB.

High Reliability Lead-free Solder Paste

Generally, the use of high reliability lead-free solder pastes can improve solder joint strength when compared with a standard lead-free solder paste. However, Nichia does not recommend using them as a measure to reduce solder cracks since it may cause stress to become concentrated onto the LEDs leading to cracks and/or breakage of the LED chip. When selecting a solder paste, perform sufficient verifications with the chosen PCB taking into consideration the conditions/environments in which the LEDs will actually be used to ensure there are no issues.

This document contains tentative information, Nichia may change the contents without notice.

### 4. Precautions for Setting Up a Pick-and-Place Machine/Nozzle

Table 8. Cautions/Suggestions for Setting Up Equipment

Item	Recommended Conditions/Specifications	Cautions/Suggestions
Pick-and-place machine	Modular mounter	See the note below this table.
Pick-and-Place Nozzle	Specially designed nozzle (see Figure 3)	See "Pick-and-Place Nozzle" on Page 9 for the details.
Tape-and-reel feeder	Electrical (motorized) feeder Tape width: 8mm Feeder pitch: 4mm	See "Tape-and-Reel Feeder" on Page 10 for the details.
Top Cover Tape Removal Position	Immediately before pick-up	See "Tape-and-Reel Feeder" on Page 10 for the details.
Nozzle height for pick-up operations	The contact surface of the nozzle head for pick operations should be adjusted to 0.3mm below the edge of the embossed carrier tape pocket.	See "Recommended Nozzle Height for Pick-up Operations" on Page 11 for the details.
Nozzle height for placement operations (i.e. placement depth)	0.2mm for placement depth	See "Recommended Nozzle Height for Placement Operations (Placement Depth)" on Page 11 for the details.
Imaging-based Automatic Inspection	Using the electrode as a reference is recommended to locate the center of the LEDs.	See "Imaging-based Automatic Inspection" on Page 12 for the details.

Note:

- The recommended conditions/specifications above have been determined under the following verification conditions:  
Pick-and-place machine (modular mounter):  
- YS100 High-Speed General-Purpose Modular (manufactured by Yamaha Motor Co., Ltd.)

This document contains tentative information, Nichia may change the contents without notice.

## 4.1 Pick-and-Place Nozzle

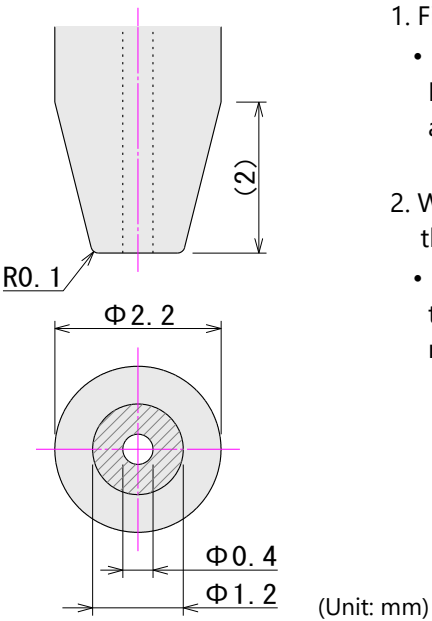


Figure 3. Recommended Nozzle Dimensions

- Figure 3 shows the recommended dimensions for the pick-and-place nozzle.
  - Ensure that the size and shape of the nozzle tip are appropriate for the LEDs. Otherwise, this may damage the LEDs (i.e. scratch, chip, crack, etc.), affecting the optical characteristics and/or the reliability. This may also lead to an incorrect pick up (i.e. the LEDs are picked up in a tilted position).
- When setting the LED pick-up position, ensure that the center of the nozzle and the center of the emitting area of the LEDs are aligned (See Figure 3). Do not apply excessive force to the emitting area when picking up the LEDs.
  - If the nozzle does not pick up the LEDs at the center of the emitting area, and/or if excessive force is applied to the LEDs, this may damage the LEDs (i.e. scratch, chip, crack, etc.), affecting the optical characteristics and/or the reliability. This may also lead to an incorrect pick up (i.e. the LEDs are picked up in a tilted position).




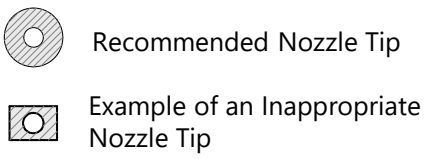


Figure 4. Examples of LED pick-up positions for the Nichia 131G/131H Series LEDs

This document contains tentative information, Nichia may change the contents without notice.


## 4.2 Tape-and-Reel Feeder

- It is **recommended** to remove the top cover tape immediately before LED pick-up.

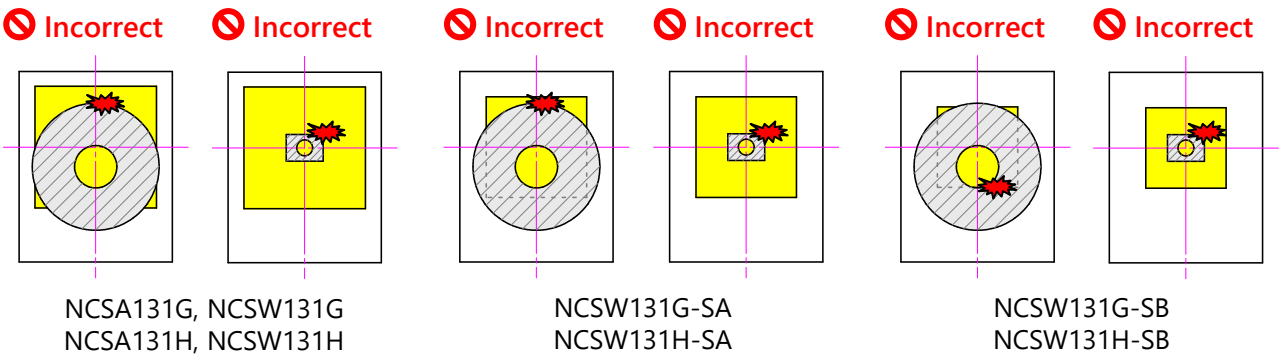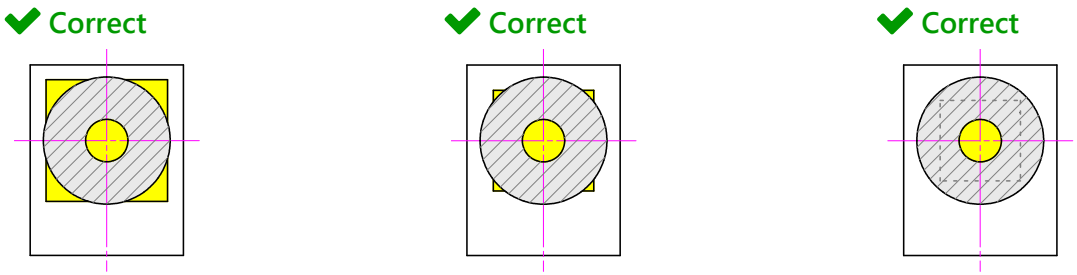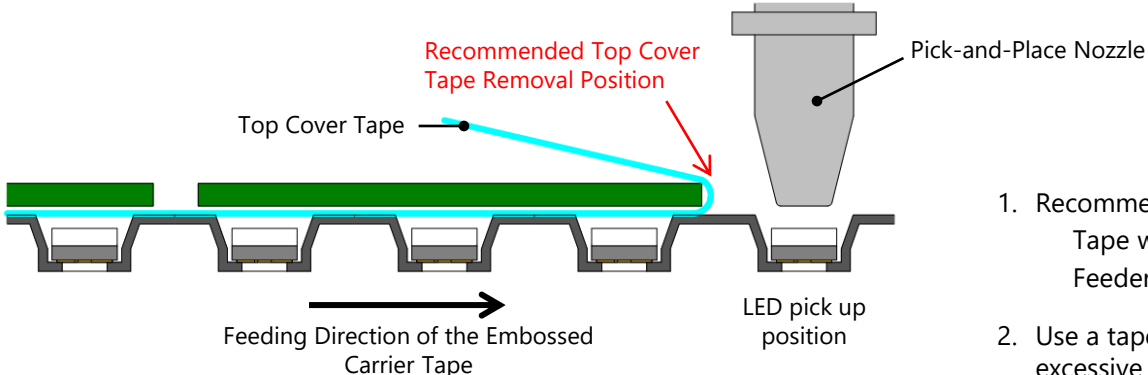

1. Recommended setting for the tape-and-reel feeder.  
Tape width: 8mm  
Feeder pitch: 4mm
2. Use a tape-and-reel feeder that ensures it does not create excessive vibrations causing assembly issues.  
Example: Electrical (motorized) feeder

- It is **NOT recommended** to remove the top cover tape at a point significantly far away from the LED pick-up position.

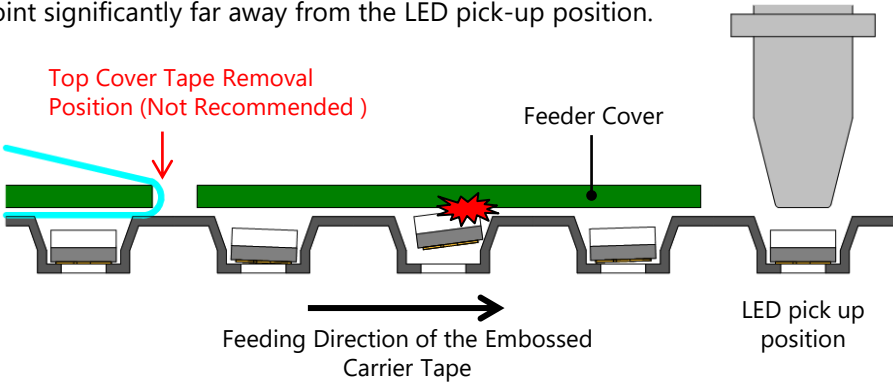

- When the tape feeder feed rate is fast, the LEDs in the embossed carrier tape pockets may not be in the correct position when picked by the nozzle; it may be improved by reducing the tape feeder feed rate.
3. It is recommended to remove the top cover tape immediately before the LED pick-up position.
- If the tape is removed at a point significantly far away from the LED pick-up position, the LED may contact the feeder cover causing damage to the emitting surface.

Figure 5. Top Cover Tape Removal Position

## 4.3 Recommended Nozzle Height for Pick-up Operations

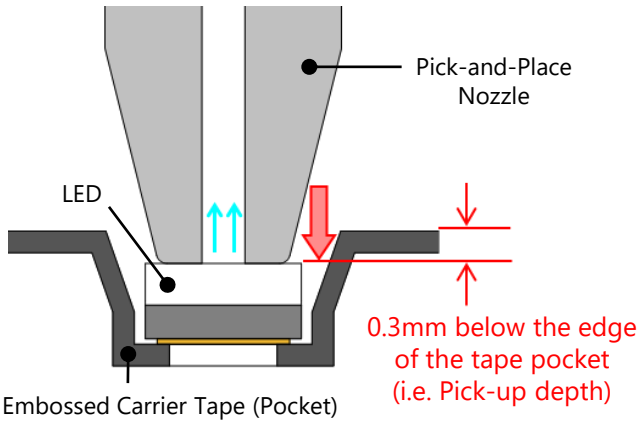


Figure 6. Recommended Nozzle Height for Pick-up Operations

1. Ensure that the nozzle goes down onto the LEDs in the tape pocket until the tip touches LEDs.  
Pick-up depth: 0.3mm  
Note: If the reference level for the nozzle setting is at the edge of the tape pocket.
2. The recommended nozzle height for pick-up operations has been determined by Nichia under the verification conditions (See Table 8) and may not function as expected with some other pick-and-place machines. If the pick-up operations are unstable even with using the recommended nozzle height, adjust the nozzle height appropriate for the pick-and-place machine being used.  
  
If the pick point of the nozzle is too high,
  - it may cause insufficient suction power leading to picking errors (e.g. the nozzle's failure to pick/lift the LEDs into the air, incorrect picking causing the LEDs to tilt when in the air).  
If the pick point of the nozzle is too low,
  - it may cause issues (e.g. causing the embossed carrier tape to shake, causing the tape pocket to deform) leading to picking failure.

## 4.4 Recommended Nozzle Height for Placement Operations (Placement Depth)


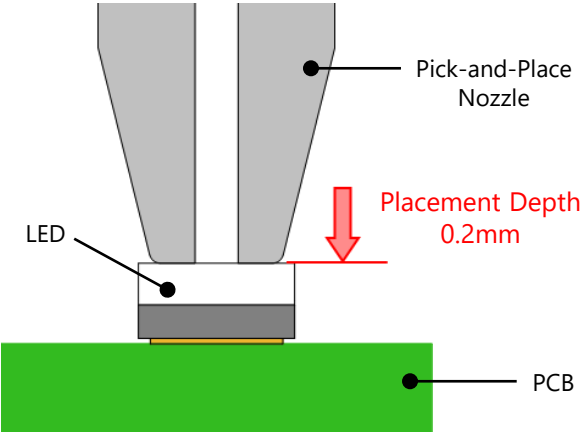


Figure 7. Recommended Nozzle Height for Placement (Placement Depth)

1. The nozzle should further press the LEDs 0.2mm onto the PCB from the height where the LEDs first touch solder paste.  
  
If the release point of the nozzle is too high,
  - it may cause placement issues (e.g. the LEDs to stick to the nozzle after placement, the LEDs to be mounted in an incorrect place/rotated position, the LEDs to become soldered to the PCB in a tilted position, etc.).  
If the release point of the nozzle is too low,
  - excessive forces may be applied to the LEDs during placement and it may cause the LEDs to become damaged.

This document contains tentative information, Nichia may change the contents without notice.

## 4.5 Imaging-based Automatic Inspection

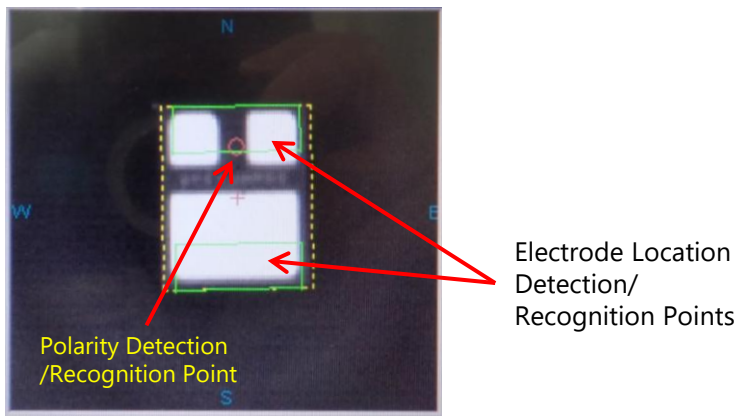

1. Nichia recommends using the electrodes as a reference to locate the center of the LEDs.
2. If the imaging device has trouble detecting/recognizing the electrodes, adjust the settings (i.e. the brightness of the light, etc.) of the pick-and-place machine.

Figure 8. Recommended Reference Points to Detect, Recognize, or Locate the Electrodes

## 5. Precautions When Reflow Soldering

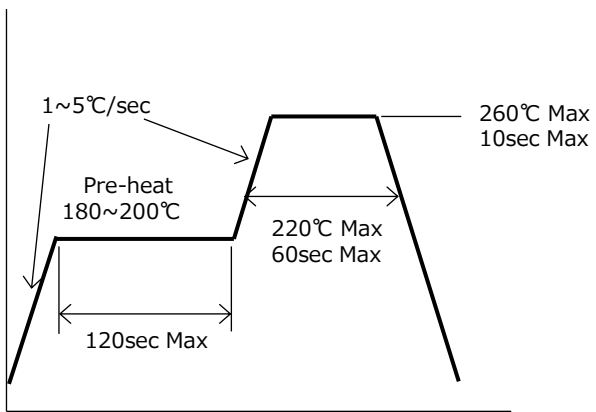


Figure 8. Recommended Reflow Soldering Condition (Lead-free Solder)

1. Reflow soldering must not be performed more than twice.
2. Nichia recommends using the reflow soldering conditions detailed in Figure 8 to the left; use the recommended reflow conditions specified by the manufacturer of the solder paste being used if it works better for the chosen application.

Note: To ensure that these reflow conditions have no negative effect on the LEDs, perform sufficient verification prior to use.

3. When cooling the LEDs from the peak temperature a gradual cooling slope is recommended; do not cool the LEDs rapidly.
4. During reflow soldering, the heat and atmosphere in the reflow oven may cause the optical characteristics to degrade. In particular, reflow soldering performed with an air atmosphere may have a greater negative effect on the optical characteristics than if a nitrogen atmosphere is used; Nichia recommends using a nitrogen reflow atmosphere.
5. If the amount of solder voids in the solder joint is large, solder cracks may be likely to occur, etc. causing an effect on the reliability of the end-product. If the amount of solder voids is large, adjust the reflow conditions to reduce the amount of solder voids.

This document contains tentative information, Nichia may change the contents without notice.

### 6. Evaluation of the Effect of Solder Conditions

Nichia evaluated the effect of solder volume for reflow-soldering the LEDs (i.e. the parallel/angular deviations and self-alignment performance) using different solder conditions including the recommended conditions as shown in Section 3.

- PCB and LEDs Used for the Evaluation
  - FR4, copper layer thickness of 70μm, substrate thickness of 1.6mm, LED Part No.: NCSW131G, Sample Size: 250 LEDs per condition for the placement accuracy, 15 LEDs per condition for the self-alignment performance
- Evaluated Items
  - Placement accuracy (x and y directions, angular direction, and tilt) and self-alignment performance (x and y directions and rotation)

Table 9. Soldering Pad Patterns, Metal Solder Stencil Apertures, and Solder Volumes

	Recommended Condition	Different Conditions		
Thickness	100μm	80μm	100μm	120μm
Soldering Pad Pattern (NSMD)				
Metal Solder Stencil Aperture				


- Center of the Soldering Pad Pattern
- Copper Layer
- Solder Mask Aperture
- Soldering Pad Pattern
- Metal Solder Stencil Aperture
- LED Outline
- Electrodes and Die Heat Sink

(Unit: mm)


This document contains tentative information, Nichia may change the contents without notice.

## 6.1 Placement Accuracy in x and y Directions


Nichia evaluated the placement accuracy of the reflow-soldered LEDs in the x and y directions from the center of the soldering pad pattern using different solder conditions. The amount of the deviation from the center of the soldering pad pattern in the x and y directions are described as  $\Delta x$  and  $\Delta y$  respectively. Sample size: 250 LEDs per condition



+ : Centerline of the emission area  
 + : Target LED Position

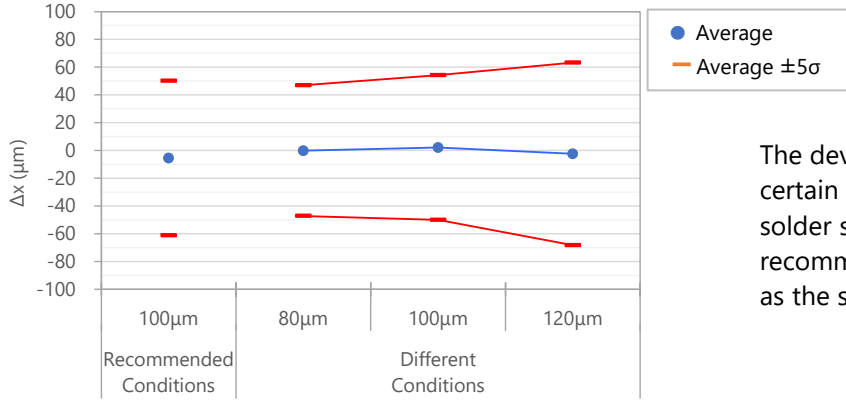


The deviation of  $\Delta x$  of the evaluated LEDs was improved to a certain extent when the soldering pad pattern and the metal solder stencil aperture used were different from the recommended conditions. The deviation tended to be smaller as the solder volume decreased.

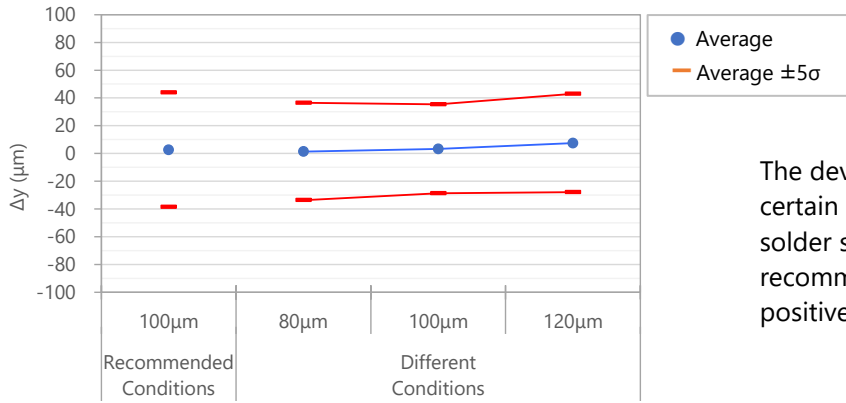


The deviation of  $\Delta y$  of the evaluated LEDs was improved to a certain extent when the soldering pad pattern and the metal solder stencil aperture used were different from the recommended conditions. The LEDs tended to shift toward the positive side a little as the solder volume increased.

## 6.2 Placement Accuracy in the Angular Direction

Nichia evaluated the placement accuracy of the reflow-soldered LEDs in the angular direction from the reference axis of the soldering pad pattern using different solder conditions. The amount of the deviation from the reference axis in the angular direction is described as  $\Delta\theta$ . Sample size: 250 LEDs per condition





+ : Centerline of the emission area  
 + : Reference Axis

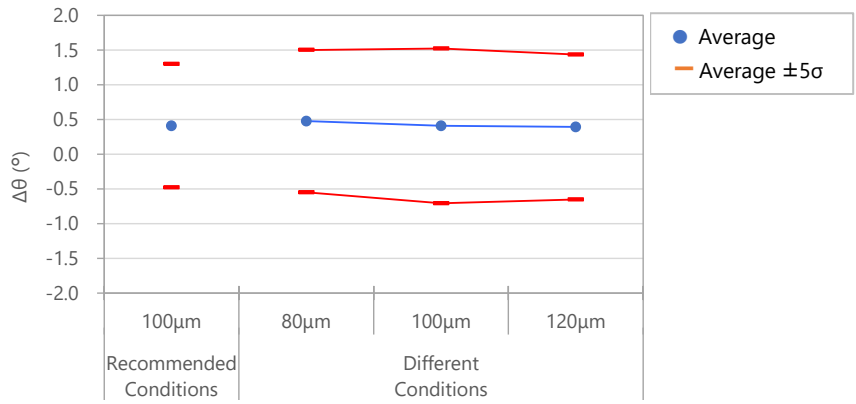

The deviation of  $\Delta\theta$  of the evaluated LEDs became slightly larger when the soldering pad pattern and the metal solder stencil aperture used were different from the recommended conditions. There was no significant difference seen when the solder volumes were changed from the recommended conditions by changing the thickness of the metal solder stencil.



## 6.3 Placement Accuracy in the Angular Direction ( $\Delta Z\theta$ )

Nichia evaluated the placement accuracy of the reflow-soldered LEDs in the z direction (i.e. tilt in the height direction) from the center of the soldering pad pattern using different solder conditions. The amount of the deviation from the center of the soldering pad pattern in the z-x and z-y directions are described as  $\Delta Z\theta$ . Sample size: 250 LEDs per condition

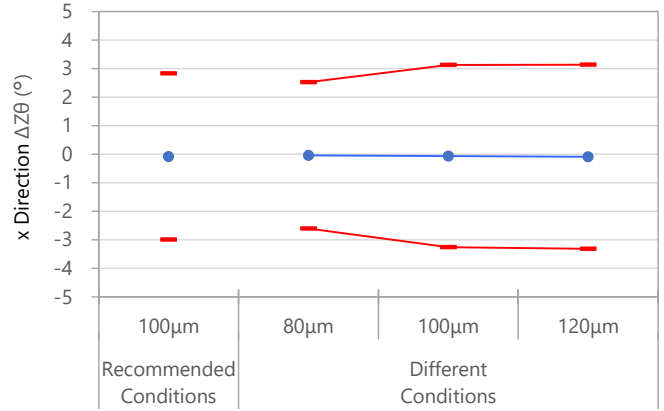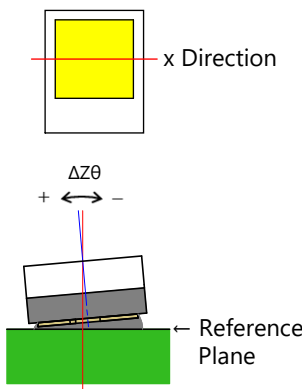

● Average  
— Average  $\pm 5\sigma$

The deviation of  $\Delta Z\theta$  of the evaluated LEDs in the z-x direction did not become smaller by using a soldering pad pattern and a metal solder stencil aperture that differed from the recommended conditions. The deviation tended to be smaller as the solder volume decreased.

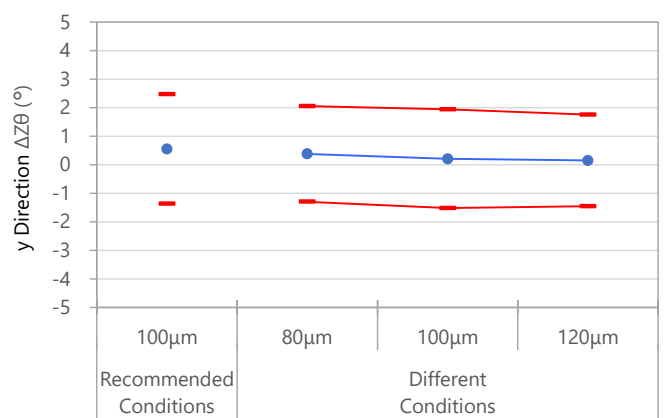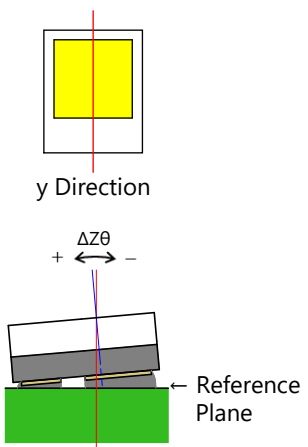


● Average  
— Average  $\pm 5\sigma$

The deviation of  $\Delta Z\theta$  of the evaluated LEDs in the z-y direction became smaller when the soldering pad pattern and the metal solder stencil aperture used were different from the recommended conditions. There was no significant difference seen when the solder volumes were changed from the recommended conditions by changing the thickness of the metal solder stencil.



## 6.4 Self-alignment Performance in the x and y Directions

Nichia evaluated the self-alignment performance of the reflow-soldered LEDs using different solder conditions: the evaluation LEDs were placed on specified points (i.e.  $x = -200\mu\text{m}$  and  $y = +200\mu\text{m}$ / $x = -200\mu\text{m}$  and  $y = -200\mu\text{m}$  from the center of the soldering pad pattern). Sample Size: 15 LEDs per condition

**Evaluated LED Placement Position 1**

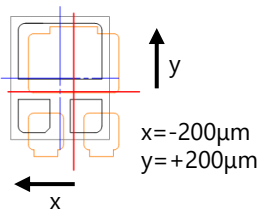


- : Soldering Pad Pattern
- + : Center of the Soldering Pad Pattern
- + : Center of the Evaluated LED Placement Position

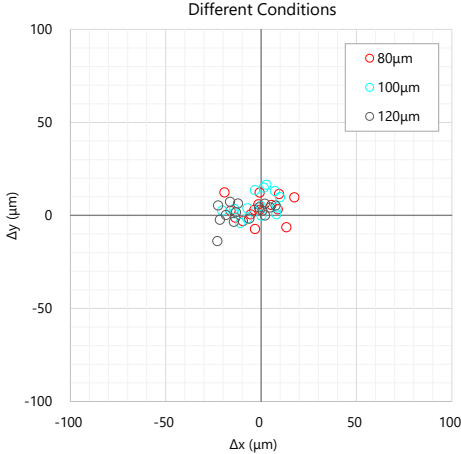
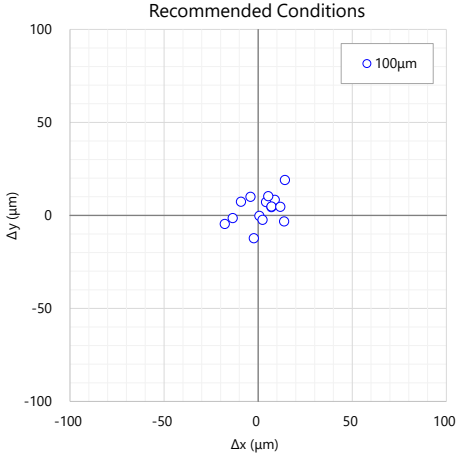


With all the evaluation conditions used, the LEDs moved to positions that were sufficiently close to the correct one (i.e. the amount of the deviation was almost the same as the evaluation results shown in 6-1); there were no issues.

**Evaluated LED Placement Position 2**

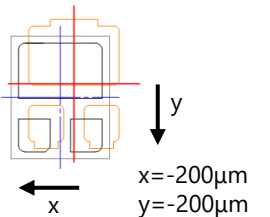

- : Soldering Pad Pattern
- + : Center of the Soldering Pad Pattern
- + : Center of the Evaluated LED Placement Position

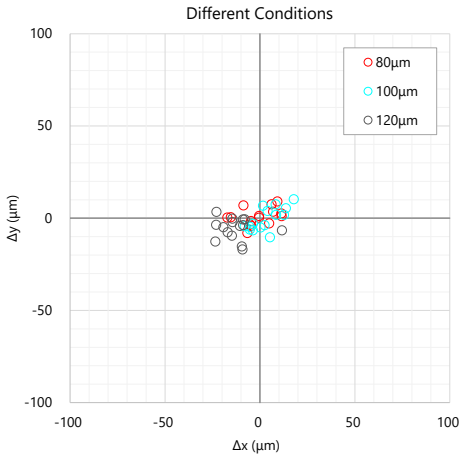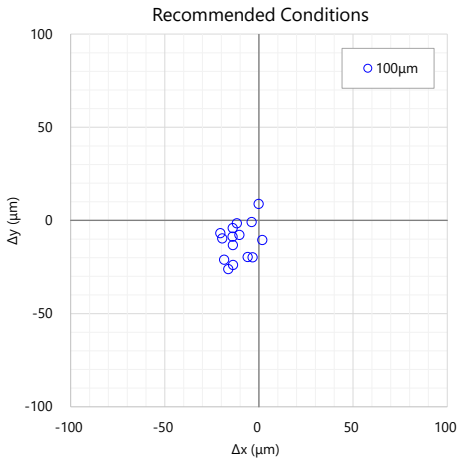


With all the evaluation conditions used, the LEDs moved to positions that were sufficiently close to the correct one (i.e. the amount of the deviation was almost the same as the evaluation results shown in 6-1); there were no issues.

This document contains tentative information, Nichia may change the contents without notice.



## 6.5 Self-alignment Performance in the Angular Direction

Nichia evaluated the self-alignment performance of the reflow-soldered LEDs using different solder conditions: the evaluation LEDs were intentionally rotated (i.e.  $\Delta\theta = -5/10^\circ$  from the reference axis whose origin was the center of the soldering pad pattern). Sample Size: 15 LEDs per condition

**Evaluated LED Placement Position 3**

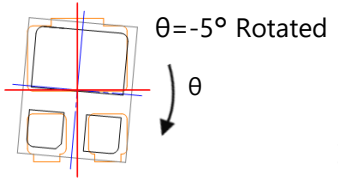


- : Soldering Pad Pattern
- + : Reference Axis of the Soldering pad pattern
- + : Reference Axis of the Evaluated LED Placement Position

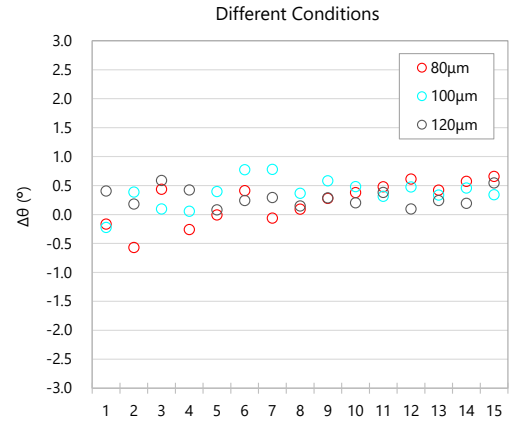
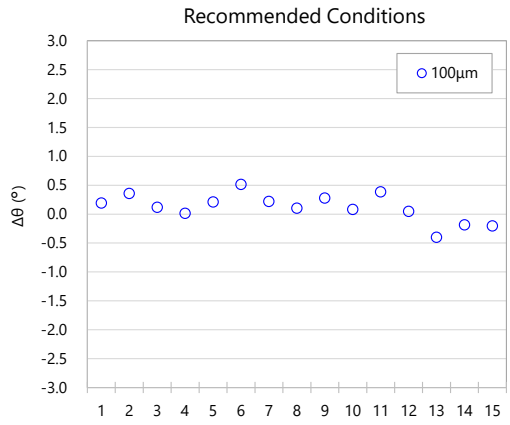


With all the evaluation conditions used, the LEDs moved to positions that were sufficiently close to the correct one (i.e. the amount of the deviation was almost the same as the evaluation results shown in 6-2); there were no issues.

**Evaluated LED Placement Position 4**

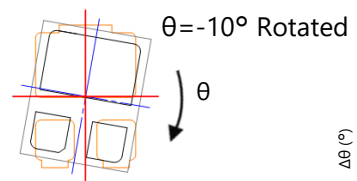

- : Soldering Pad Pattern
- + : Reference Axis of the Soldering pad pattern
- + : Reference Axis of the Evaluated LED Placement Position

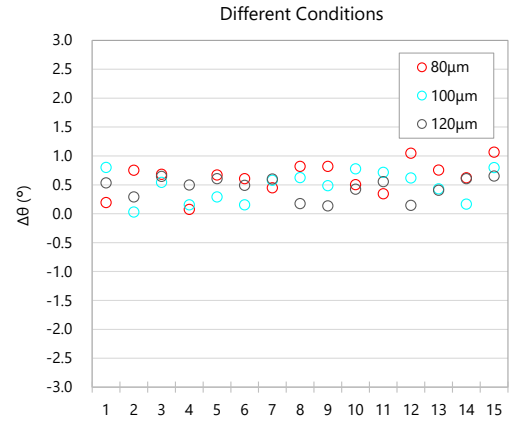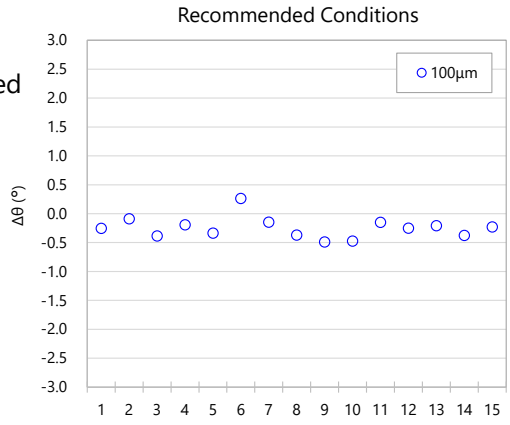

With all the evaluation conditions used, the LEDs moved to positions that were sufficiently close to the correct one (i.e. the amount of the deviation was almost the same as the evaluation results shown in 6-2); there were no issues.

This document contains tentative information, Nichia may change the contents without notice.

## 6.6 Summary

- The evaluation results show that overall, the placement accuracy tends to be better when the solder volume is smaller. However, if the solder volume is insufficient, it may cause a decrease in solder joint strength.
- The evaluation results provided herein were affected by the manufacturing accuracy of the PCB, the precision of the measurement instruments, etc.; these results should be used for reference purposes only.
- The evaluation results provided herein were obtained under Nichia's evaluation conditions/environments; Nichia makes no guarantee that customers will see the same results for their chosen application. Perform a sufficient verification to ensure that there are no issues with the chosen conditions/environments.

## Disclaimer

This application note is a controlled document of Nichia Corporation (Nichia) published to provide technical information/data for reference purposes only. By using this application note, the user agrees to the following:

- This application note has been prepared solely for reference on the subject matters incorporated within it and Nichia makes no guarantee that customers will see the same results for their chosen application.
- The information/data contained herein are only typical examples of performances and/or applications for the product. Nichia does not provide any guarantees or grant any license under or immunity from any intellectual property rights or other rights held by Nichia or third parties.
- Nichia makes no representation or warranty, express or implied, as to the accuracy, completeness or usefulness of any information contained herein. In addition, Nichia shall not be liable for any damages or losses arising out of exploiting, using, or downloading or otherwise this document, or any other acts associated with this document.
- The content of this application note may be changed without any prior or subsequent notice.
- Copyrights and all other rights regarding the content of this document are reserved by Nichia or the right holders who have permitted Nichia to use the content. Without prior written consent of Nichia, republication, reproduction, and/or redistribution of the content of this document in any form or by any means, whether in whole or in part, including modifications or derivative works hereof, is strictly prohibited.

**NICHIA CORPORATION** 491 Oka, Kaminaka-Cho, Anan-Shi,  
TOKUSHIMA 774-8601, JAPAN  
<http://www.nichia.co.jp> Phone: +81-884-22-2311 Fax: +81-884-21-0148

This document contains tentative information, Nichia may change the contents without notice.